

# Polycrystalline Thin-Film Multijunction Solar Cells

R. Noufi, X. Wu, J. Abu-Shama, K. Ramanathan,  
R. Dhere, J. Zhou, T. Coutts, M. Contreras,  
T. Gessert, and J.S. Ward

*Presented at the 2005 DOE Solar Energy Technologies  
Program Review Meeting  
November 7–10, 2005  
Denver, Colorado*

**Conference Paper**  
**NREL/CP-520-39002**  
**November 2005**

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



## NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy  
Office of Scientific and Technical Information  
P.O. Box 62  
Oak Ridge, TN 37831-0062  
phone: 865.576.8401  
fax: 865.576.5728  
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce  
National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161  
phone: 800.553.6847  
fax: 703.605.6900  
email: [orders@ntis.fedworld.gov](mailto:orders@ntis.fedworld.gov)  
online ordering: <http://www.ntis.gov/ordering.htm>



# Polycrystalline Thin-Film Multijunction Solar Cells

R. Noufi, X. Wu, J. Abu-Shama, K. Ramanathan, R. Dhere, J. Zhou,  
T. Coutts, M. Contreras, T. Gessert, J.S. Ward  
National Renewable Energy Laboratory, Golden, CO 80401

## ABSTRACT

We present a digest of our research on the thin-film material components that comprise the top and bottom cells of three different material systems and the tandem devices constructed from them.

### 1. Objectives

Develop approaches toward improving transparent top cells, and an appropriate bottom cell to demonstrate a 25%-efficient polycrystalline thin-film tandem solar cell.

### 2. Technical Approach

We focused on three areas of exploration:

- Top cell: Three material systems to be evaluated, CGS, CdTe, and CdMgTe. The top cell is the more-critical component in a dual-junction tandem cell, expected to deliver about two-thirds of the power.
- Bottom cell: Optimize the CIS device (bandgap  $E_g \sim 1$  eV) as a bottom cell, with emphasis on red response.
- Available choices for interconnecting the top and bottom cell: Assess the performance of the different components in a dual-junction thin-film device.

### 3. Salient Results

We provide salient results for the three top cell materials, and one bottom-cell material.

#### 3.1 Top Cell

##### A. CdTe-based top cell

We have shown previously through modeling that it is possible to achieve a 25% all-thin-film dual-junction tandem device by using a top-cell bandgap in the range of 1.5 to 1.8 eV, where 1.7 eV is optimum. In the short term, this allows us to use a transparent CdTe-based cell as the top cell, with a 15% CIS bottom cell.

In the study of thin CdTe cells and transparent CdTe cells, we found that the conventional graphite paste or ZnTe:Cu back-contact are not suitable for device fabrication of thin CdTe or transparent CdTe cells. We developed a novel three-step process for producing a  $\text{Cu}_x\text{Te}$  back-contact, which includes: (1) produce a Te-rich layer by chemical etch, (2) deposit thin Cu (or Cu alloy), and (3) post-heat anneal to form  $\text{Cu}_x\text{Te}$  layer. We also tried to understand the following: (1) the stoichiometry of  $\text{Cu}_x\text{Te}$  film prepared by the three-step

process, (2)  $\text{Cu}_x\text{Te}$  thickness control and its effect on device performance, (3)  $\text{Cu}_x\text{Te}$  phase control and its effect on device performance, and (4) stability of  $\text{Cu}_x\text{Te}$  back-contact with different thickness and phase.

We have successfully applied a  $\text{Cu}_x\text{Te}$  back-contact to fabricate a high-efficiency transparent CdTe cell as a top cell in a four-terminal tandem solar cell. In the past, almost all R&D activities in this area focused on developing a transparent back-contact with  $E_g$  larger than the  $E_g$  of the top cell, such as ZnTe:Cu or ZnTe:N with  $E_g$  of  $\sim 2.26$  eV, or ITO with  $E_g$  of  $\sim 3.9$  eV. The best result is a 10.1%-efficient CdTe cell with a ZnTe:Cu back-contact that has a 60%–85% film transmission in the near-infrared (NIR) region. However, we exploited a thinner  $\text{Cu}_x\text{Te}$  back-contact and modified device structure to fabricate high-efficiency poly-CdTe thin-film solar cells with higher NIR transparency. We fabricated several CTO/ZTO/nano-CdS:O/CdTe/ $\text{Cu}_x\text{Te}$ /ITO/Ni-Al grid cells with efficiencies of more than 13% by this technique. The best cell has an NREL-confirmed, total-area efficiency of 13.94% ( $V_{oc} = 806.1$  mV,  $J_{sc} = 24.94$  mA/cm<sup>2</sup>, FF = 69.22%, and area = 0.41 cm<sup>2</sup>) with  $\sim 60\%$ – $40\%$  transmission in the wavelength range of 860–1300 nm. We also produced a CdTe/CIS polycrystalline thin-film tandem cell with an NREL-confirmed total-area efficiency of 15.3%, exceeding the FY 2006 milestone in DOE/NREL's HiPerf PV project.

##### B. CGS-based top cell

We measured a new total-area record efficiency of 10.23% for modified  $\text{CuGaSe}_2$  solar cells. This improvement resulted from a modified three-stage growth process of the absorber layer, with more Cu-rich conditions in the second stage and the addition of  $<1\%$  of In at the end of the third stage. This modified growth resulted in higher current density and better quantum efficiency in the 10.23% cell, and may have made the surface of the modified CGS absorber similar to that of CIGS. The density of surface defects in the modified CGS cell is lower than that in the 9.53% cell. The modified CGS has a stronger (220/204) preferred orientation in the bulk, compared to that in the 9.53% CGS. We observed a Cu-depleted surface layer within the top part of the 10.23% modified CGS film, with composition close to that of the  $\text{Cu}_1(\text{In,Ga})_3\text{Se}_5$  phase. The best 4-terminal tandem

device using CGS/SnO<sub>2</sub> as a top cell and CdS/CIS as a bottom cell gave an efficiency of 9.7% with  $V_{oc} = 1.29$  V.

### C. CdMgTe-based top cell

CdMgTe thin films are a new candidate for a top cell. The Cd<sub>1-x</sub>Mg<sub>x</sub>Te alloy system has several advantages: (1) large range of energy gap that allows material in the 1.6–1.8-eV range, with the least amount of Mg addition (5%–25%), (2) least deviation from the lattice constant of CdTe (tetrahedral radius, CdTe = 2.81 Å, MgTe = 2.76 Å), and (3) linear variation of bandgap with Mg. The limited amount of work done on these alloys has not explored them for polycrystalline thin films. A number of approaches were tried for depositing these alloys. Co-deposition using CdTe and MgCl<sub>2</sub>, deposition from pre-alloyed Cd<sub>1-x</sub>Mg<sub>x</sub>Te source material, and co-deposition of CdTe and MgF<sub>2</sub> were attempted, but were unsuccessful. We succeeded when we co-deposited CdTe and Mg. We were able to vary the composition over a wide range by adjusting the relative rates of deposition of the two sources. Figure 1 shows the dependence of the energy gap on the Mg content. A linear relationship is observed, and the regression fit can be describe by:  $E_g = 1.54 x + 1.1$  eV.

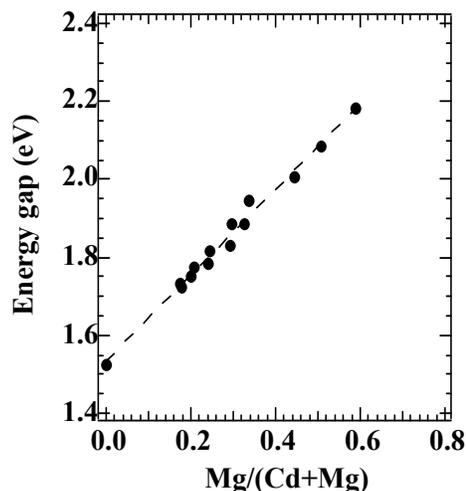


Fig. 1. Energy gap as a function of Mg content for Cd<sub>1-x</sub>Mg<sub>x</sub>Te alloy thin films.

The results presented here accord with earlier reports on bulk alloy materials and are the first, to our knowledge, for the polycrystalline materials. This is an ongoing project and we are initiating solar cell fabrication work incorporating Cd<sub>1-x</sub>Mg<sub>x</sub>Te alloy films. Our objective is to demonstrate efficient solar cells operating in the 1.6–1.8 eV range.

### 3.2 Bottom Cell

To date, we have leveraged the optimization of the performance of CIGS-based solar cells carried out under the polycrystalline thin-film CIGS project to improve the efficiency of the CuInSe<sub>2</sub>-based device (1 eV) used as the bottom cell for two-junction tandems. We demonstrated a 15.1% solar cell. At this point, the performance is maximized for the objective of this project; therefore, we will shift some of the effort to enhance improvement to the CGS (1.7 eV) top cell.

### ACKNOWLEDGEMENTS

The work was performed for the U.S. DOE PV Program under Contract No. DE-AC36-99GO10337 to NREL. The authors wish to thank J. Dolan, T. Moriarty, and colleagues in the Measurements and Characterization Division for their assistance in this work.

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

**PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.**

<b>1. REPORT DATE (DD-MM-YYYY)</b> November 2005		<b>2. REPORT TYPE</b> Conference Paper		<b>3. DATES COVERED (From - To)</b>	
<b>4. TITLE AND SUBTITLE</b> Polycrystalline Thin-Film Multijunction Solar Cells				<b>5a. CONTRACT NUMBER</b> DE-AC36-99-GO10337	
				<b>5b. GRANT NUMBER</b>	
				<b>5c. PROGRAM ELEMENT NUMBER</b>	
<b>6. AUTHOR(S)</b> R. Noufi, X. Wu, J. Abu-Shama, K. Ramanathan, R. Dhere, J. Zhou, T. Coutts, M. Contreras, T. Gessert, and J.S. Ward				<b>5d. PROJECT NUMBER</b> NREL/CP-520-39002	
				<b>5e. TASK NUMBER</b> PVA6.4301	
				<b>5f. WORK UNIT NUMBER</b>	
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> NREL/CP-520-39002	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>				<b>10. SPONSOR/MONITOR'S ACRONYM(S)</b> NREL	
				<b>11. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>12. DISTRIBUTION AVAILABILITY STATEMENT</b> National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161					
<b>13. SUPPLEMENTARY NOTES</b>					
<b>14. ABSTRACT (Maximum 200 Words)</b> We present a digest of our research on the thin-film material components that comprise the top and bottom cells of three different material systems and the tandem devices constructed from them.					
<b>15. SUBJECT TERMS</b> Photovoltaics; solar; polycrystalline; thin film ; multijunction solar cell; PV; NREL					
<b>16. SECURITY CLASSIFICATION OF:</b>			<b>17. LIMITATION OF ABSTRACT</b> UL	<b>18. NUMBER OF PAGES</b>	<b>19a. NAME OF RESPONSIBLE PERSON</b>
<b>a. REPORT</b> Unclassified	<b>b. ABSTRACT</b> Unclassified	<b>c. THIS PAGE</b> Unclassified			<b>19b. TELEPHONE NUMBER (Include area code)</b>