



A New Method to Characterize Degradation of First Surface Aluminum Reflectors

Preprint

Florian Sutter, Peter Heller, Stephanie Meyen,
and Robert Pitz-Paal

*DLR German Aerospace Center, Institute for Technical
Thermodynamics*

Cheryl Kennedy

National Renewable Energy Laboratory

Aránzazu Fernández-García

CIEMAT, Plataforma Solar de Almeria, Ctra.

Martin Schmücker

*DLR German Aerospace Center, Institute for Material
Sciences*

Presented at SolarPACES 2010

Perpignan, France

September 21-24, 2010

NREL is a national laboratory of the U.S. Department of Energy, Office of Energy Efficiency & Renewable Energy, operated by the Alliance for Sustainable Energy, LLC.

Conference Paper

NREL/CP-5500-49164

October 2010

Contract No. DE-AC36-08GO28308

NOTICE

The submitted manuscript has been offered by an employee of the Alliance for Sustainable Energy, LLC (Alliance), a contractor of the US Government under Contract No. DE-AC36-08GO28308. Accordingly, the US Government and Alliance retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information

P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/help/ordermethods.aspx>

Cover Photos: (left to right) PIX 16416, PIX 17423, PIX 16560, PIX 17613, PIX 17436, PIX 17721



Printed on paper containing at least 50% wastepaper, including 10% post consumer waste.

A NEW METHOD TO CHARACTERIZE DEGRADATION OF FIRST SURFACE ALUMINUM REFLECTORS

Florian Sutter¹, Aránzazu Fernández García², Peter Heller¹, Cheryl Kennedy³, Stephanie Meyen¹, Robert Pitz-Paal¹, Martin Schmücker⁴

¹Solar Researcher, DLR German Aerospace Center, Institute for Technical Thermodynamics, PSA, Ctra. Senés Km. 4, P.O.Box 44, 04200, Tabernas, Almería (Spain), +34 950 277684, Florian.Sutter@dlr.de

²Solar Researcher, CIEMAT, Plataforma Solar de Almería, Ctra. Senés Km. 4, 04200 Tabernas, Almería (Spain)

³Solar Researcher, NREL National Renewable Energy Laboratory, 1617 Cole Boulevard, Golden, CO 80401-3393 USA

⁴Material Scientist, DLR German Aerospace Center, Institute for Material Sciences, Linder Höhe, D-51147 Cologne, Germany

Abstract

This paper reports the development of a new optical instrument capable of characterizing the aging process of enhanced first surface aluminum reflectors for concentrating solar power (CSP) application. Samples were exposed outdoors at different sites and in accelerated exposure tests. All samples exposed outdoors showed localized corrosion spots. Degradation originated from points of damage in the protective coating, but propagated underneath the protective coating. The degraded samples were analyzed with a microscope and with a newly designed space-resolved specular reflectometer (SR)² that is capable of optically detecting and characterizing the corrosion spots. The device measures the specular reflectance at three acceptance angles and the wavelengths with spatial resolution using a digital camera's CMOS sensor. It can be used to measure the corrosion growth rate during outdoor and accelerated exposure tests. These results will allow a correlation between the degraded mirror surface and its specular reflectance.

Keywords: accelerated and outdoor weathering, aging of reflectors, specular reflectance, reflectometer, filiform corrosion of aluminum, soiling

1. Introduction

Radiation emitted by the sun is focused onto the absorber tube of a parabolic trough collector with solar mirrors if the aperture angle of the reflected beam is less than 20 mrad (half-cone angle (Fig.1a)). Including collector tracking, absorber tube position, and mirror slope errors, reflector surface scattering within a 12.5 mrad angle is acceptable for a parabolic trough collector [1].

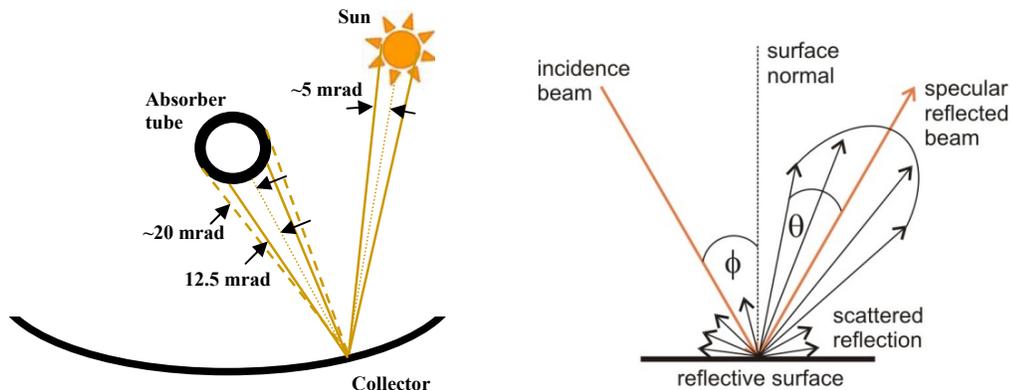


Fig. 1. a) Specular reflectance at a parabolic trough collector and b) definition of terms

The Alliance for Sustainable Energy, LLC (Alliance), is the manager and operator of the National Renewable Energy Laboratory (NREL). Employees of the Alliance, under Contract No. DE-AC36-08G028308 with the U.S. Dept. of Energy, have authored this work. The United States Government retains and the publisher, by accepting the article for publication, acknowledges that the United States Government retains a non-exclusive, paid-up, irrevocable, worldwide license to publish or reproduce the published form of this work, or allow others to do so, for United States Government purposes.

Specular reflectance is the amount of light reflected into the acceptance half angle θ shown in Fig.1b. Reflectance is dependent on the wavelength (λ), the angle of incidence (ϕ) that incoming light makes with the mirror surface normal, and the acceptance half angle (θ) that marks the greatest offset of a reflected beam to the ideal specular reflected beam. Hemispherical reflectance can be understood as the reflectance within an acceptance half angle of π . Reflectance is written with all three parameters $\rho(\lambda, \phi, \theta)$. The most important parameter to evaluate if a reflector material is suited for concentrating solar power (CSP) parabolic trough application is its solar-weighted specular reflectance value at 12.5 mrad. Other important parameters for solar mirrors are their cost and their resistance to weathering with a required durability of at least 20 years.

The specular reflectance is usually measured with a field portable 15R specular reflectometer from Devices and Services Instruments (D&S). Measurements can be taken at different half-cone acceptance angles (3.5, 7.5, and 12.5 mrad), one certain wavelength $\lambda = 660$ nm, and $\phi=15^\circ$. The solar-weighted specular reflectance value can be approximated using a standard terrestrial solar spectrum [2] and the solar weighting formula described in [2, 3].

The existing instruments used to measure the specular reflectance have several disadvantages in terms of characterizing degradation processes: the measuring spot is usually very small (~ 1 cm in diameter), the measurements can only be taken at one specified wavelength, and the measurements are not spatially resolved. For reflectors that degrade locally, several measurements are necessary to statistically evaluate the influence of degradation on the reflectance properties. Problems associated with the measurement of specular reflectance are also described in [4].

2. Space-resolved specular reflectometer (SR)²

In order to monitor and optically characterize local degradation, the space-resolved specular reflectometer (SR)² was developed (Fig.2) [5]. The major advantage of the (SR)² compared to other reflectometers is the possibility of measuring the specular reflectance on an extended measuring spot of 5.5 cm with a spatial resolution of 12 pixel/mm. Additionally, measurements can be taken at three different acceptance half angles ($\theta = 3.5, 7.5,$ and 12.5 mrad) and at three different wavelengths ($\lambda = 410$ nm, 500 nm, and 656 nm).

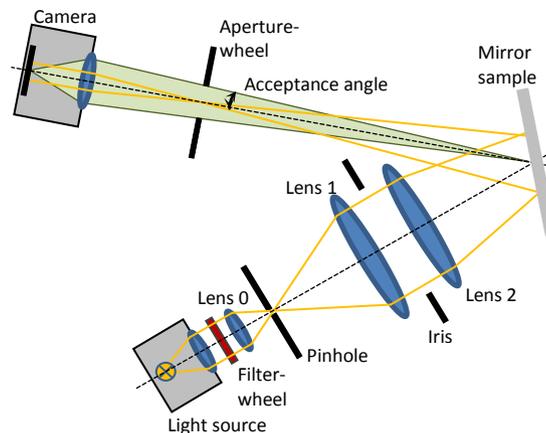


Fig. 2. Space-resolved specular reflectometer (SR)² instrument scheme

The parallel light emitted from a 75W xenon arc lamp is focused onto a 2-mm pinhole. The light passing through the pinhole is collected by two achromatic lenses that focus the beam into the center of the aperture wheel. To measure the specular reflectance, the mirror sample is placed in the optical path and held in place by vacuum suction to a flat plate. The sample holder design reduces the uncertainty due to mirror slope errors. The acceptance angle is changed by rotating the aperture wheel. The instrument is designed so that all of the light passing through the aperture falls onto the complementary metal-oxide-semiconductor (CMOS) sensor of the digital camera. Measurements are taken in a dark room to avoid errors through ambient diffuse light. The prototype of the system is shown in Fig.3a and b.

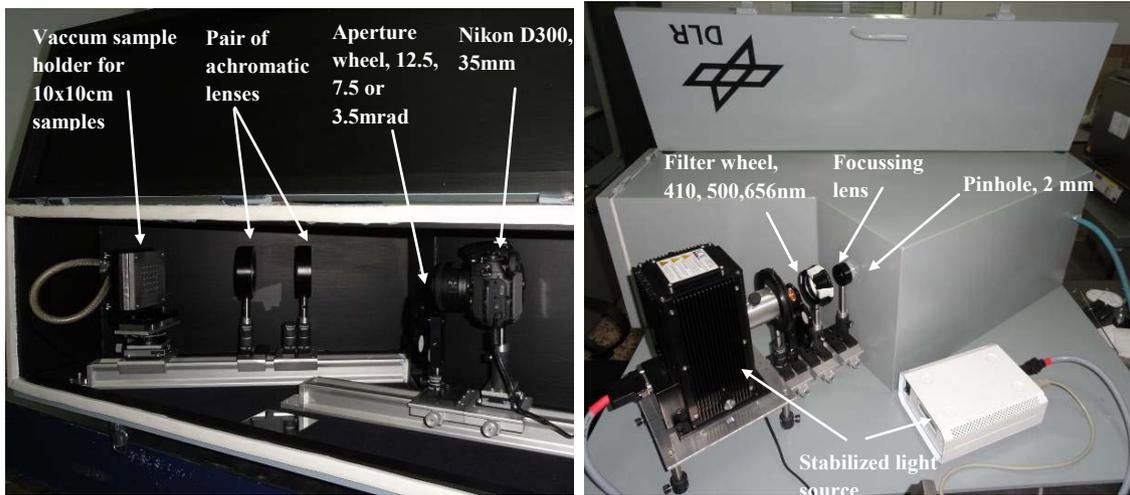


Fig. 3. Prototype at DLR a) interior view of the dark box, b) exterior view

The photographs obtained in RAW-format are linearized and converted to ppm format with the open source software *dcrw*. In the linear photograph, the number of photons that fall on each pixel is proportional to the pixel intensity. The instrument is calibrated with a reference mirror for which the specular and hemispherical reflectance properties are identical ($\rho_{\text{specular},\lambda} = \rho_{\text{hem},\lambda}$). The $\rho_{\text{specular},410\text{nm}}$, $\rho_{\text{specular},500\text{nm}}$, and $\rho_{\text{specular},656\text{nm}}$ can then be determined using the Perkin-Elmer Lambda1050 UV-Vis-NIR spectrophotometer. Measurements taken in the (SR)² are corrected for errors from dust on the optical components or inhomogeneous illumination of the mirror sample by using a reference photograph of the calibration mirror.

The instrument can be employed to evaluate the surface reflectance characteristics of flat mirrors with the creation of a reflectance map. In combination with aging tests, the instrument can monitor gradual changes like the growth of degradation (Fig.4). The fraction of degraded surface relative to the intact surface of the mirror can be evaluated as well. The instrument can also be used to characterize the scattering from soiled mirrors before and after cleaning.

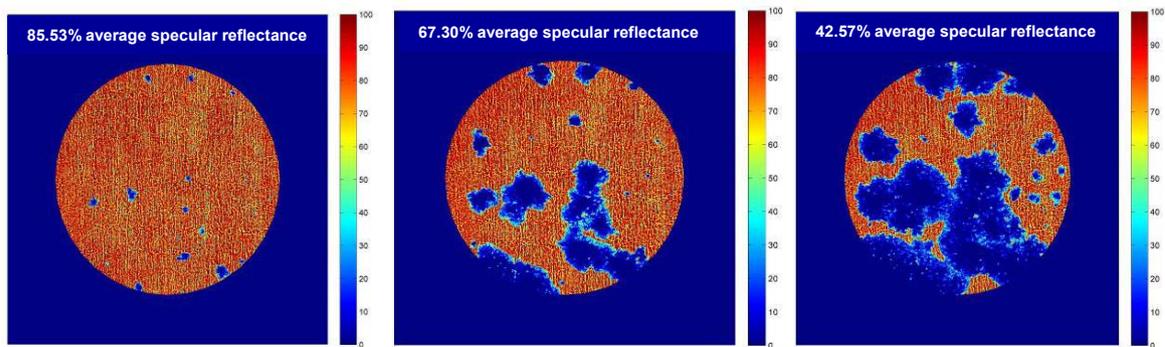


Fig. 4. Corrosion monitoring of accelerated testing to determine the corrosion growth rate and its effect on specular reflectance. (Reflectance map at $\lambda = 656\text{nm}$, $\phi = 15^\circ$ and $\theta = 12.5\text{ mrad}$, blue = 0%, red=100% specular reflectance)

3. Aging analysis of a first surface enhanced aluminum reflector

Aggressive cost reductions and performance improvements in the solar field are required for CSP technologies with thermal storage to produce electricity competitively. This has led to the study of solar reflector candidate materials with the potential to reduce cost, weight, and installation labor while increasing optical performance and durability.

One such promising solar reflector candidate is the enhanced first surface aluminum mirror shown in Fig.5. The polished aluminum substrate is anodized, and a pure aluminum layer is deposited by physical vapor

deposition (PVD). The reflectance of the aluminum is enhanced by $\frac{1}{4}$ wavelength thick, low- and high-index-of-refraction oxide coatings and protected with a sol-gel nanocomposite oxide layer. The initial solar-weighted hemispherical reflectance is 91.8%; initial specular reflectance at 12.5-mrad half angle and 660 nm is 83.7% and at 3.5-mrad is 71.7%.

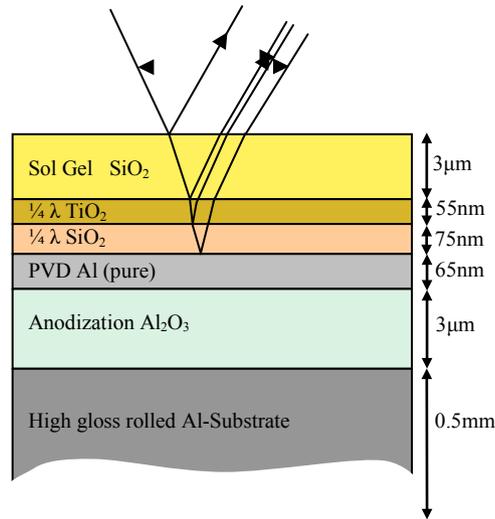


Fig. 5. Composition of the enhanced aluminum reflector

3.1. Outdoor weathering

Samples of the enhanced aluminum reflector were exposed at three outdoor test sites in Phoenix, Arizona (APS), Golden, Colorado (NREL), and Miami, Florida (FLA) in the United States. Outdoor exposure sites in Europe were in Cologne, Germany (KOL) and Tabernas, Spain (TAB). All materials are optically characterized prior to exposure testing and as a function of exposure time to assess optical durability.

3.2. Accelerated weathering

Two accelerated exposure chambers were used at NREL: an Atlas Ci5000 WeatherOmeter (WOM) and a BlueM damp-heat accelerated exposure chamber (BlueM). The Ci5000 WOM uses a two-sun xenon-arc light source with filters designed to closely match the terrestrial AM1.5 global solar spectrum. The Ci5000 operates continuously at 60°C and 60% relative humidity (RH). A single day of testing (24 hours) in the Ci5000 is roughly equivalent to six times outdoors. The BlueM operates continuously without light at 85°C and 85% RH. While the BlueM does not have the same measurable acceleration factor as the WOMs, from experiments, the acceleration factor approaches 25 times outdoors.

The solar-weighted hemispherical and specular reflectance over exposure time at the different exposure sites and in the accelerated exposure chambers is shown in Fig.6.

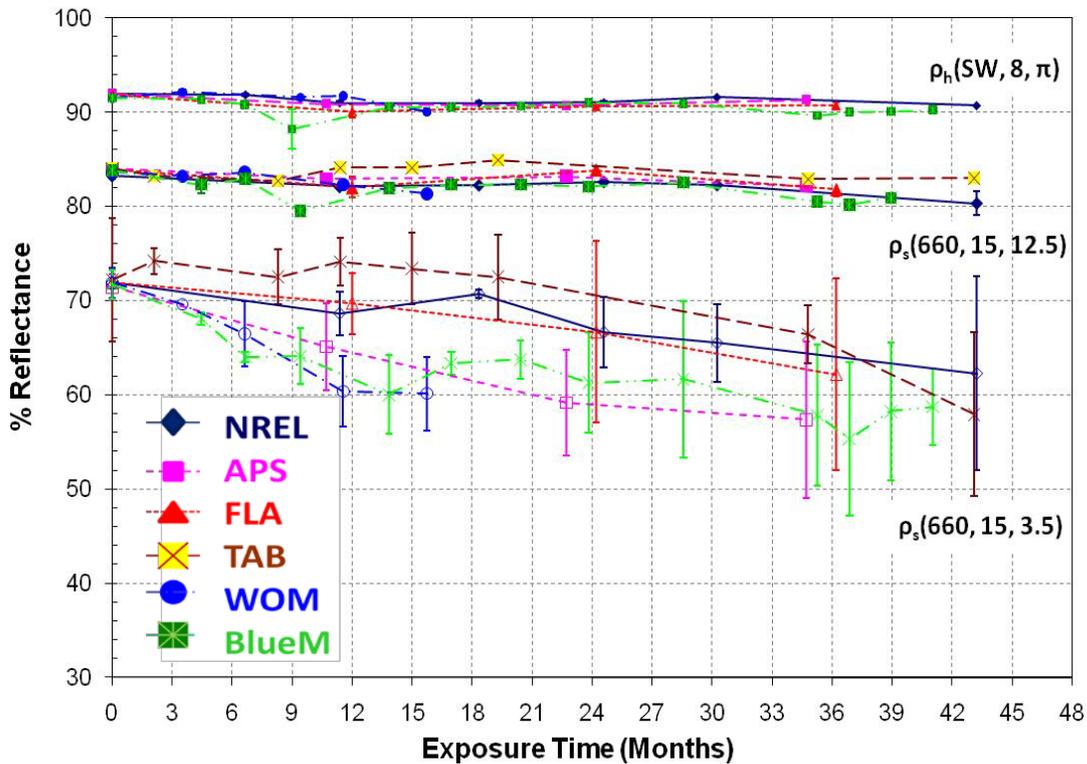


Fig.6: Solar-weighted hemispherical reflectance (SWH) and specular reflectance at $\theta = 3.5$ and 12.5 mrad at $\lambda = 660\text{nm}$ of enhanced aluminum reflectors after accelerated exposure in BlueM (dark / 85°C / $85\%\text{RH}$), WOM (2 sun / 60°C / $60\%\text{RH}$) chambers, and outdoor exposure at NREL, APS, FLA, and TAB.

3.3. Degradation mechanism

After three years of outdoor exposure at the different sites, only slight decreases in the solar-weighted hemispherical reflectance (SWH) can be observed. The specular reflectance at 3.5 mrad shows a maximum loss of 14.1% after 34.7 months of exposure in Phoenix. However, the specular reflectance within the 12.5mrad acceptance angle is more relevant for parabolic trough applications. Here, losses are only in the range of $1\text{-}2\%$ after three years of exposure.

Small corrosion spots were observed by visual or microscopic inspection on all samples exposed at every outdoor site. The corrosion starts at coating defects such as micro-cracks, coating break outs or pinholes (Fig. 7a and 7b).

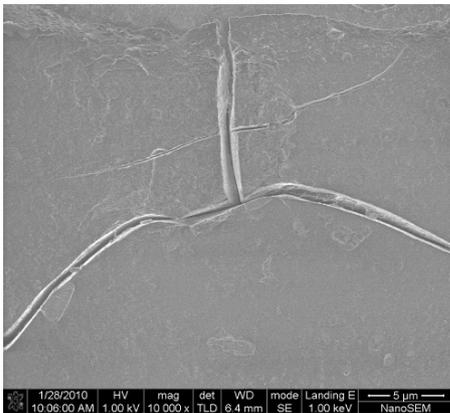


Fig. 7a. Crack in protective coating viewed in the SEM

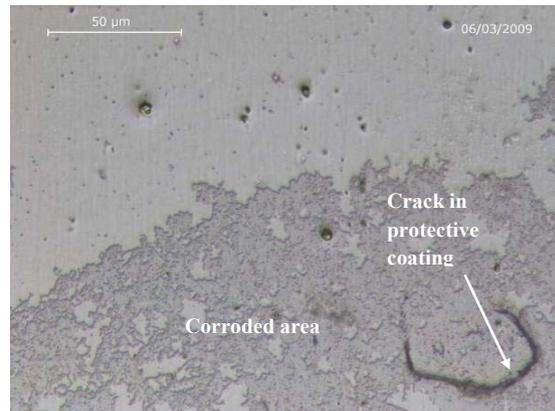


Fig. 7b. Filiform corrosion and crack viewed in the light microscope

A cross section image reveals that the degradation occurs at the pure aluminum layer (Fig.8). The image was produced with a transmission electron microscope (TEM) in Z-Contrast mode (the intensity is proportional to the atomic number Z). The sample preparation occurred by focused ion beam (FIB) to avoid introducing new defects. Other attempts to prepare the sample (like polishing or grinding) were not successful because the blade caused delamination of the sample's coating.

A vertical energy-dispersive X-ray spectroscopy (EDX) line scan with high spatial resolution detected a loss of the aluminum in the degraded areas. The void is able to propagate underneath the SiO₂ and TiO₂ enhancing layers, while they themselves remain unharmed. This effect is also known as filiform corrosion. The natural corrosion mechanism observed in samples exposed outdoors was not reproduced in the accelerated weathering chambers. More germane accelerating test methods are still being developed.

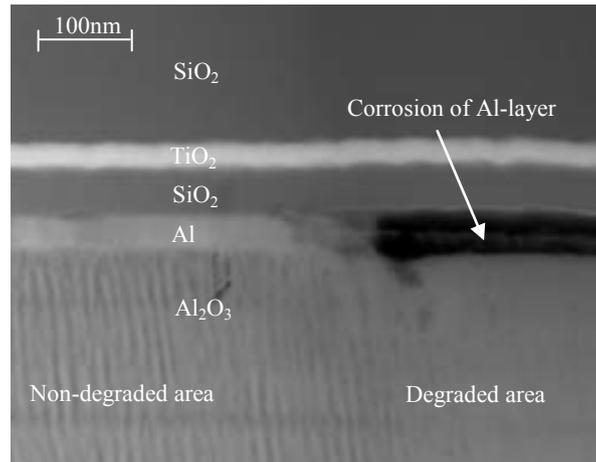


Fig.8: Cross section of a corrosion spot

4. Optical characterization of corrosion processes with the space-resolved specular reflectometer (SR)²

The new instrument measures the following parameters through image analysis:

- Average specular reflectance of the measurement spot of the sample
- Fraction of area with specular reflectance below a boundary value (selected by user)
- Detection of local corrosion spots and evaluation of their area and specular reflectance
- Specular reflectance of non-corroded area.

The new instrument has been used to measure samples of the enhanced aluminum reflector exposed for 57 months outdoors in Tabernas and for 36 months in Miami. The specular reflectance, the corroded mirror area, the number of corrosion spots, and the specular reflectance of the non-corroded area are shown in Fig. 9 for both sites. The given values are mean values averaged from two samples per site. The initial specular reflectance was $\rho_s(660\text{nm}, 15^\circ, 12.5\text{mrad}) = 83.7\%$ measured with the D&S. Samples measured after 36 months of exposure in Miami, $\rho_s(660\text{nm}, 15^\circ, 12.5\text{mrad}) = 81.8\%$ with the D&S and with the (SR)² $\rho_s(656\text{nm}, 15^\circ, 12.5\text{mrad}) = 81.8\%$. After 57 months of exposure in Tabernas, $\rho_s(660\text{nm}, 15^\circ, 12.5\text{mrad}) = 81.2\%$ for samples measured with the D&S and $\rho_s(656\text{nm}, 15^\circ, 12.5\text{mrad}) = 81.4\%$ measured with the (SR)². The results show that Miami is a more aggressive environment than Tabernas because the corroded mirror surface area is almost twice as big in a shorter period of time. Local corrosion accounts for a loss in specular reflectance of 0.4% in Tabernas and 1.1% in Miami.

In future work, samples exposed at Köln, Germany and in salt spray chambers will be evaluated for the influence of climatic conditions on corrosion kinetics. The corrosion growth rates will be determined as a function of climatic conditions through periodic monitoring.

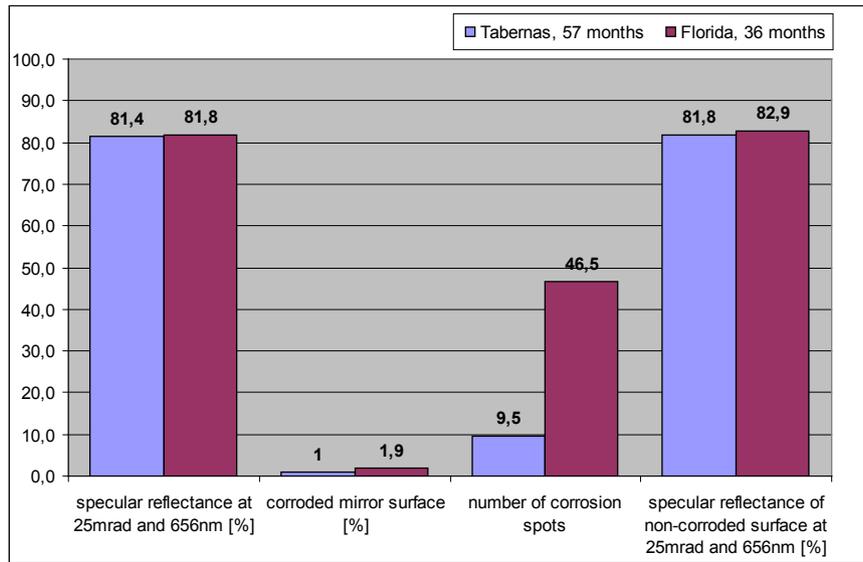


Fig.9: Optical characterization of four samples of the enhanced aluminium reflector exposed for 57 months in Tabernas, Spain and 36.1 months in Miami, USA. (Initial specular reflectance was 83.7%)

5. Optical characterization of soiling processes of a glass mirror with the space-resolved specular Reflectometer (SR)²

The new instrument can also be employed to determine the cleanliness factor of mirror samples and to characterize the scattering due to soiling. The device was used to measure a new glass mirror exposed for 22 days in Tabernas, Spain both in soiled condition and after being cleaned. The mirror surface area whose reflectance is less than a defined boundary value can be determined from the curves in Fig.10. For example, it can be seen that 91.4% of the mirror surface has a reflectance less than 70% when soiled, whereas after being cleaned, only 0.001% of the surface has a reflectance less than 70%.

The average specular reflectance of the soiled surface was $\rho(656\text{nm}, 15^\circ, 12.5\text{mrad}) = 52.3\%$; after being cleaned it was $\rho_s(656\text{nm}, 15^\circ, 12.5\text{mrad}) = 95.2\%$. Thus the cleanliness factor χ (as ratio of ρ_{soiled} to ρ_{clean}) is $\chi = 0.55$. The measurements show good agreement with D&S readings. The larger measurement spot (5.5cm in diameter for the (SR)² compared to 1cm for the D&S) has benefits because inhomogeneous soiling requires a statistical evaluation of the surface.

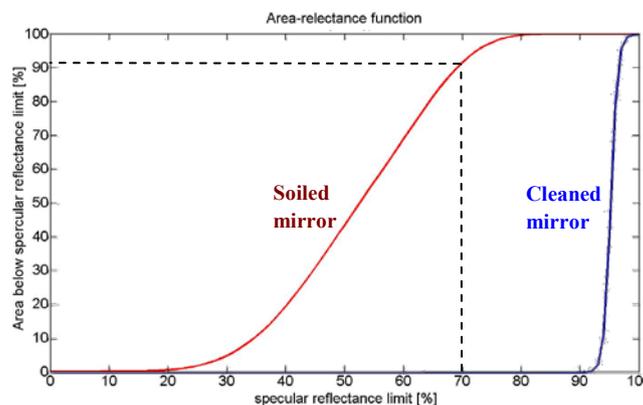


Fig.10: Area-reflectance dependency for a new glass mirror (soiled in Tabernas, Spain for 22 days and cleaned afterwards; measurements at 656nm, 15° incidence angle, and 12.5mrad)

6. Conclusion and Outlook

A new instrument has been designed to measure spatially resolved specular reflectance. The method is suited to characterize local corrosion and soiling processes of solar reflectors. Analysis of an enhanced aluminum reflector with the new (SR)² instrument showed that the reflectance loss of the mirror is mainly due to local corrosion and scattering. Microscope analysis showed that the pure aluminum layer corrodes underneath the unharmed protective and enhancing coatings. Samples exposed in Miami, United States corrode faster than samples exposed in Tabernas, Spain.

In future work, samples exposed in the United States and Europe will be periodically monitored in order to determine corrosion growth rates as a function of climatic conditions. With this data, simplified service lifetime prediction models can be derived to predict the reflectance losses during long-term exposure.

Acknowledgements

The authors want to thank Gary Jorgensen (NREL), Robert Tirawat (NREL), Sebastian Hübener (DLR), and José Rubio (DLR) for their support. NREL's part of this work was performed under DOE contract DE-AC36-99-GO10337.

References

- [1] R. B. Pettit, "Characterization of Reflected Beam Profile of Solar Mirror Materials," *Solar Energy*, Vol. 19, No. 6, 1977, pp. 773-741.
- [2] ASTM Standard G 173 – 03, "Standard Tables for Reference Solar Spectral Irradiances: Direct Normal and Hemispherical on 37° Tilted Surface," *Annual Book of ASTM Standards 2008*, Vol. 14.04. West Conshohocken, PA: American Society for Testing and Materials.
- [3] DIN Standard 5036, Part 1, "Radiometric and photometric properties of materials: Definitions and characteristic factors," July 1978, Berlin, Germany: Deutsches Institut für Normung e.V.
- [4] S. Meyen, A. Fernandez, C. Kennedy, E. Lüpfer, "Standardization of Solar Mirror Reflectance Measurements – Round Robin Test," to be published in *Proceedings SolarPaces Symposium Perpignon, 2010*
- [5] *Deutsche Patentanmeldung* "Vorrichtung und Verfahren zur Bestimmung von Reflexionseigenschaften eines Reflektors," F. Sutter, P. Heller, S. Meyen, C. Prah, June 2010

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.

1. REPORT DATE (DD-MM-YYYY) October 2010			2. REPORT TYPE Conference Paper			3. DATES COVERED (From - To)		
4. TITLE AND SUBTITLE A New Method to Characterize Degradation of First Surface Aluminum Reflectors: Preprint					5a. CONTRACT NUMBER DE-AC36-08GO28308			
					5b. GRANT NUMBER			
					5c. PROGRAM ELEMENT NUMBER			
6. AUTHOR(S) F. Sutter, P. Heller, S. Meyen, R. Pitz-Paal; DLR German Aerospace Center, Institute for Technical Thermodynamics A. F. García; CIEMAT, Plataforma Solar de Almeria, Ctra. M. Schmücker; DLR German Aerospace Center, Institute for Material Sciences C. Kennedy; NREL					5d. PROJECT NUMBER NREL/CP-5500-49164			
					5e. TASK NUMBER CP09.8101			
					5f. WORK UNIT NUMBER			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393					8. PERFORMING ORGANIZATION REPORT NUMBER NREL/CP-5500-49164			
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)					10. SPONSOR/MONITOR'S ACRONYM(S) NREL			
					11. SPONSORING/MONITORING AGENCY REPORT NUMBER			
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161								
13. SUPPLEMENTARY NOTES								
14. ABSTRACT (Maximum 200 Words) This paper reports the development of a new optical instrument capable of characterizing the aging process of enhanced first surface aluminum reflectors for concentrating solar power (CSP) application. Samples were exposed outdoors at different sites and in accelerated exposure tests. All samples exposed outdoors showed localized corrosion spots. Degradation originated from points of damage in the protective coating, but propagated underneath the protective coating. The degraded samples were analyzed with a microscope and with a newly designed space-resolved specular reflectometer (SR)2 that is capable of optically detecting and characterizing the corrosion spots. The device measures the specular reflectance at three acceptance angles and the wavelengths with spatial resolution using a digital camera's CMOS sensor. It can be used to measure the corrosion growth rate during outdoor and accelerated exposure tests. These results will allow a correlation between the degraded mirror surface and its specular reflectance.								
15. SUBJECT TERMS accelerated and outdoor weathering; aging of reflectors; specular reflectance; reflectometer; filiform corrosion of aluminum; soil								
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON			
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)			